

This technical specification aims to define the chemical/mechanical properties and standards for cold rolled grade 304 stainless steel strips.

Grade 304 Stainless Steel Strips Technical Specifications

1. 304 Stainless Steel Strips Chemical Composition

Grade	Spec.	Range	%C	%Si	%Mn	%P	%S	%Cr	%Ni	%Mo	%Ti	%N
304	ASTM A240	Min.						18.00	8.00	-	-	-
		Max.	0.07	0.75	2.00	0.045	0.030	20.00	11.00	-	-	0.10

Stainless Steel Grade Comparison

STS	USA	UNS	CHINA	EURONORM		RUSSIA	SWEDISH	JAPANESE
GRADE	AISI/ASTM	NO	GB	NO	NAME	GOST	SS	JIS
304	304	S30400	06Cr18Ni9	1.4301	X6CrNi1810	08KH18N10 06KH18N11	2332	SUS 304

Any hard copy in your possession should be considered not up-to-date. Contact with WUXI HZW TECHNOLOGY Quality Department for up-to-date document. More information, please visit our website <https://www.metalstripsolutions.com> or send us mail sales@metalstripsolutions.com at any time.

This technical specification aims to define the chemical/mechanical properties and standards for cold rolled grade 304 stainless steel strips.

2. 304 Stainless Steel Strips Mechanical Properties

Grade	EN Grade	Yield Strength Rp0.2 (N/mm ²)	Tensile Strength Rm (N/mm ²)	Hardness	Vickers Hardness (HV)	Elongation A80 % Min.
304	1.4301	≥205	≥520	ANN	Max200	≥40
		≥450	≥700	1/4 Hard	220-250	≥20
		≥700	≥850	1/2 Hard	250-310	≥8
		≥880	≥1000	3/4 Hard	310-370	≥4
		≥1020	≥1150	Full Hard	≥370	≥1



304 STAINLESS STEEL STRIPS

TECHNICAL SPECIFICATION

HZW-304-A

Page 3/9

Date 10/05/2022

This technical specification aims to define the chemical/mechanical properties and standards for cold rolled grade 304 stainless steel strips.

3. 304 Stainless Steel Strips Shipping Mark

- Below information must be mentioned on each 304 stainless steel strips marking (shipping mark)

Supplier:		Customer:	
Alloy/Steel Grade:		Edge:	
Surface Finish:		Package No.:	
Materials Heat No.:		Net Weight:	
Size:		Gross Weight:	
Coil Quantity:		Date:	

Any hard copy in your possession should be considered not up-to-date. Contact with WUXI HZW TECHNOLOGY Quality Department for up-to-date document. More information, please visit our website <https://www.metalstripsolutions.com> or send us mail sales@metalstripsolutions.com at any time.



304 STAINLESS STEEL STRIPS

TECHNICAL SPECIFICATION

HZW-304-A

Page 4/9

Date 10/05/2022

This technical specification aims to define the chemical/mechanical properties and standards for cold rolled grade 304 stainless steel strips.


4. 304 Stainless Steel Strips Standard Packaging

- 1) Cardboard/inner core inner diameter: 300/400/500mm.
- 2) Each coil net weights to be within 500 kg. Max gross weight of each wooden pallet 1200 Kg.
- 3) Overall diameter of each coil should not exceed 1100mm.
- 4) All coils to have no splices or joints.
- 5) Material to be consistent throughout each coil, especially width, thickness and formability.
- 6) Wooden pallet with coils packed eye to sky with 40mm spacers between coils and an identification label with information relating to material.
- 7) To be supplied on pallets with a minimum leg height of 100mm.
- 8) Coils must be stored and transported in a dry environment to minimise condensation.

Any hard copy in your possession should be considered not up-to-date. Contact with WUXI HZW TECHNOLOGY Quality Department for up-to-date document. More information, please visit our website <https://www.metalstripsolutions.com> or send us mail sales@metalstripsolutions.com at any time.

This technical specification aims to define the chemical/mechanical properties and standards for cold rolled grade 304 stainless steel strips.

COIL B (Width)	OD		ID
	ØD MAX	ØD MIN	Ød
000-500mm	1100mm	600mm	200mm/300mm/400mm/500mm

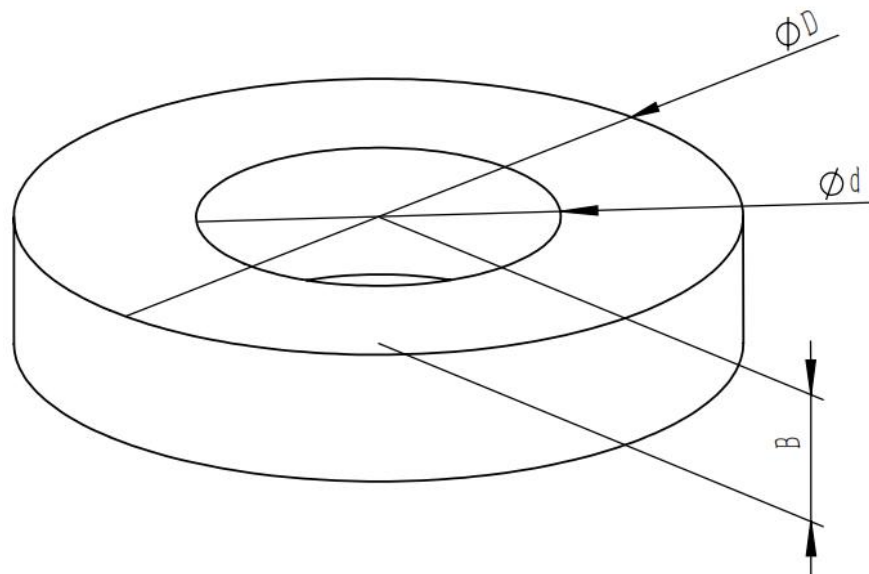


This technical specification aims to define the chemical/mechanical properties and standards for cold rolled grade 304 stainless steel strips.

5. 304 Stainless Steel Strips Flatness Tolerance

304 stainless steel strips flatness and edge waviness tolerances must be as customer's requested.

Thickness	HZW Standard		EN 1.4301	
	h/l	h/l in %	h/l	h/l in %
≤1mm	≤0.015	≤1.5	≤0.03	≤3.0
>1mm	≤0.015	≤1.5	≤0.02	≤2.0

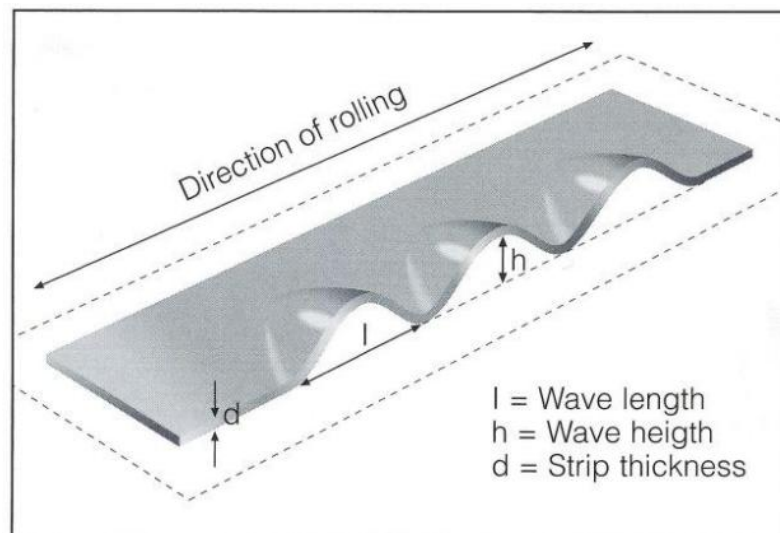


This technical specification aims to define the chemical/mechanical properties and standards for cold rolled grade 304 stainless steel strips.

6. 304 Stainless Steel Strips Straightness Tolerance

304 stainless steel strips straightness tolerance tolerances must be as customer's requested.

Width/mm		EN 1.4301 standard Straightness tolerance in mm			
≥	<	Normal		HZW Standard	
		Measured length		Measured length	
		1000mm	2000mm	1000mm	2000mm
3	10	≤ 5	≤ 20	≤ 2.5	≤ 10
10	25	≤ 4	≤ 16	≤ 1.5	≤ 6
25	40	≤ 3	≤ 12	≤ 1.25	≤ 5
40	125	≤ 2	≤ 8	≤ 1.0	≤ 4
125	400	≤ 1.5	≤ 6	≤ 0.75	≤ 3

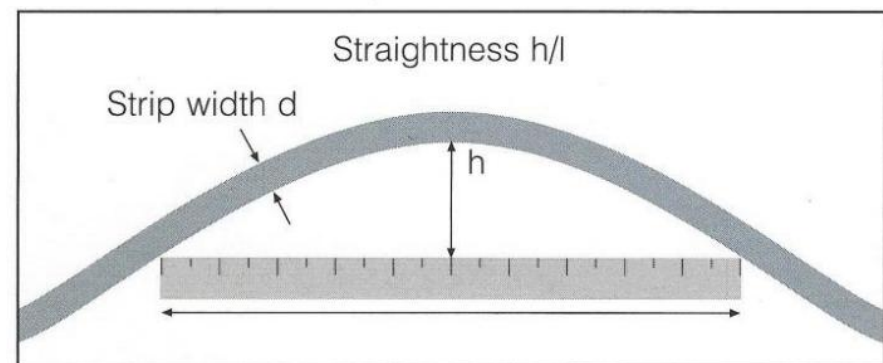

This technical specification aims to define the chemical/mechanical properties and standards for cold rolled grade 304 stainless steel strips.

7. 304 Stainless Steel Strips Thickness Tolerance

Width	JIS4305 (ET)				ASTM A240				GB/T 4239			
Thickness	<160	≥160	≥250	≥400	>5	>25	>76	>150	>20	>150	>250	>400
		<250	<400	<600	≤25	≤76	≤150	≤300	≤150	≤250	≤400	≤600
<0.10	±0.01	±0.020	-	-	±10%	±10%	0.1	±10%	±0.010	±0.010	0.01	-
≥0.10-0.16	±0.015	±0.020	-	-	±10%	±10%	0.1	±10%	±0.010	±0.010	0.01	-
≥0.16-0.25	±0.020	±0.025	±0.030	±0.030	±0.04	±0.04	0.04	±0.40	±0.010	±0.010	0.01	-
≥0.25-0.40	±0.025	±0.030	±0.035	±0.035	±0.05	±0.05	0.05	±0.06	±0.020	±0.020	±0.020	±0.020
≥0.40-0.60	±0.035	±0.040	±0.040	±0.040	±0.06	±0.06	0.06	±0.06	±0.020	0.02	±0.020	±0.030
≥0.60-0.80	±0.040td	±0.045	±0.045	±0.045	±0.06	±0.06	±0.06	±0.09	0.03	0.03	±0.030	±0.040

Any hard copy in your possession should be considered not up-to-date. Contact with WUXI HZW TECHNOLOGY Quality Department for up-to-date document. More information, please visit our website <https://www.metalstripsolutions.com> or send us mail sales@metalstripsolutions.com at any time.

This technical specification aims to define the chemical/mechanical properties and standards for cold rolled grade 304 stainless steel strips.

8. 304 Stainless Steel Strips Width Tolerance

304 Stainless Steel Strips Width Tolerance Range

Thickness	JIS4305 (EW)		ASTM A240		GB/T 4239	
	< 0.60	≥0.60-1.00	< 0.38	≥0.38-1.00	< 0.50	≥0.50-1.00
< 10	-	-	-	-	-	-
≥10-80	±0.15	±0.20	±0.127	±0.127	±0.15	±0.20
≥80-160	±0.15	±0.20	±0.127	±0.127	±0.20	±0.010
≥160-280	±0.20	±0.25	±0.254	±0.254	±0.20	±0.25
≥260-400	±0.25	±0.25	±0.254	±0.254	±0.25	±0.30
≥400-600	±0.30	±0.30	±0.406	±0.406	±0.30	±0.30

Any hard copy in your possession should be considered not up-to-date. Contact with WUXI HZW TECHNOLOGY Quality Department for up-to-date document. More information, please visit our website <https://www.metalstripsolutions.com> or send us mail sales@metalstripsolutions.com at any time.